

# Rubber- or plastics-coated fabrics — Determination of tensile strength and elongation at break

The European Standard EN ISO 1421:1998 has the status of a British Standard

ICS 59.080.40

# National foreword

This British Standard is the English language version of EN ISO 1421:1998. It is identical with ISO 1421:1998. It supersedes BS 3424-4:1982 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee TCI/78, Coated fabrics, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

### Cross-references

Attention is drawn to the fact that CEN and CENELEC Standards normally include an annex which lists normative references to international publications with their corresponding European publications. The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled “International Standards Correspondence Index”, or by using the “Find” facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

### Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN ISO title page, page 2, the ISO title page, page ii, pages 1 to 8, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

This British Standard, having been prepared under the direction of the Sector Board for Materials and Chemicals, was published under the authority of the Standards Board and comes into effect on 15 August 1998

© BSI 05-1999

ISBN 0 580 30085 4

### Amendments issued since publication

| Amd. No. | Date | Comments |
|----------|------|----------|
|          |      |          |
|          |      |          |
|          |      |          |
|          |      |          |
|          |      |          |

# Contents

|                   |                    |
|-------------------|--------------------|
|                   | Page               |
| National foreword | Inside front cover |
| Foreword          | 2                  |
| Foreword          | ii                 |
| Text of ISO 1421  | 1                  |



---

ICS

Descriptors: See ISO document

English version

## Rubber- or plastics-coated fabrics — Determination of tensile strength and elongation at break

(ISO 1421:1998)

Supports textiles revêtus de caoutchouc ou de plastique — Détermination de la force de rupture et de l'allongement à la rupture  
(ISO 1421:1998)

Mit Kautschuk oder Kunststoffe beschichtete Textilien — Bestimmung der Zugfestigkeit und der Bruchdehnung  
(ISO 1421:1998)

This European Standard was approved by CEN on 9 April 1998.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

# CEN

European Committee for Standardization  
Comité Européen de Normalisation  
Europäisches Komitee für Normung

**Central Secretariat: rue de Stassart 36, B-1050 Brussels**

Foreword

The text of the International Standard ISO 1421:1998 has been prepared by Technical Committee ISO/TC 45 “Rubber and rubber products” in collaboration with Technical Committee CEN/TC 248 “Textiles and textile products”, the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 1998, and conflicting national standards shall be withdrawn at the latest by December 1998.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of the International Standard ISO 1421:1998 was approved by CEN as a European Standard without any modification.

NOTE Normative references to International Standards are listed in Annex ZA (normative).

Contents

|   | Page              |
|---|-------------------|
| Foreword  | 2                 |
| 1 Scope   | 1                 |
| 2 Normative references  | 1                 |
| 3 Definitions   | 1                 |
| 4 Principle   | 2                 |
| 5 Apparatus   | 2                 |
| 6 Atmosphere for conditioning and testing   | 2                 |
| 7 Method 1: strip test method   | 2                 |
| 8 Method 2: grab test method  | 4                 |
| Annex ZA (normative) Normative references to international publications with their relevant European publications | Inside back cover |
| Figure 1 — Maximum force at break   | 5                 |
| Figure 2 — Tensile force at break   | 6                 |
| Figure 3 — Rupture of one element of a coated fabric  | 6                 |
| Figure 4 — Example showing how test pieces may be cut out   | 7                 |
| Figure 5 — Test piece for grab test method  | 8                 |

# INTERNATIONAL STANDARD

**ISO  
1421**

Second edition  
1998-06-15

---

---

## **Rubber- or plastics-coated fabrics — Determination of tensile strength and elongation at break**

*Supports textiles revêtus de caoutchouc ou de plastique — Détermination  
de la force de rupture et de l'allongement à la rupture*



Reference number  
ISO 1421:1998(E)

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 1421 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*.

This second edition cancels and replaces the first edition (ISO 1421:1977), which has been technically revised.

**Descriptors:** Fabrics, woven fabrics, coated fabrics, fabrics coated with rubber, fabrics coated with plastics, tests, tension tests, determination, tensile strength, elongation at break.

**WARNING — Persons using this International Standard should be familiar with normal laboratory practice. This standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.**

## 1 Scope

**1.1** This International Standard describes two methods for the determination of the tensile strength of fabrics coated with rubber or plastics:

Method 1 — the strip test method, which is a method for the determination of tensile strength and elongation at break;

Method 2 — the grab test method, which is a method for the determination of tensile strength only.

**1.2** The methods apply to test pieces in equilibrium with specific standard atmospheres for testing, and to wet test pieces.

**1.3** Both methods require the use of a constant rate of extension (CRE) tensile-testing machine.

## 2 Normative references

The following standards contains provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 2231:1989, *Rubber- or plastics-coated fabrics — Standard atmospheres for conditioning and testing*.

ISO 2286-2:1998, *Rubber- or plastics-coated fabrics — Determination of roll characteristics — Part 2: Methods for determination of total mass per unit area, mass per unit area of coating and mass per unit area of substrate*.

ISO 7500-1:1986, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tensile testing machines*.

## 3 Definitions

For the purposes of this International Standard, the following definitions apply.

### 3.1

#### maximum force

the maximum force recorded in extending the test piece to breaking point (see Figure 1)

### 3.2

#### elongation; extension (*E*)

the increase in length of a test piece, expressed in units of length, e.g. cm or mm

### 3.3

#### percentage elongation

the elongation expressed as a percentage of the nominal gauge length

### 3.4

#### force at break

the tensile force recorded at the moment of break (see Figure 2)

NOTE Figure 3 corresponds to the rupture of one of the elements constituting the coated fabric. Typical examples are:

- a) a "rigid" polymer layer on an extensible fabric: rupture of the polymer layer;
- b) a very extensible, thick polymer layer on a weak, less extensible fabric or nonwoven: rupture of the woven fabric or of the nonwoven.

### 3.5

#### elongation at break

the elongation of a test piece corresponding to the force at the breaking point (see Figure 2), usually expressed as a percentage of the nominal gauge length

### 3.6

#### nominal gauge length

the length of a test piece under a specified pre-tension, measured from nip to nip of the jaws of the holding clamps with the clamps in their starting position

NOTE The nominal gauge length is also referred to as the initial gauge length.

### 3.7

#### elongation at maximum force

the elongation of a test piece produced by the maximum force (see Figure 1)

### 3.8

#### constant rate of extension (CRE)

a means of conducting a tensile test in which the rate of increase in the length of the test piece is uniform with time

NOTE The rate of increase of the force is dependent upon the extension characteristics of the test piece.

**3.9****strip test**

a tensile strength test in which the full width of the test piece is gripped in the jaws

**3.10****grab test**

a tensile strength test in which only the central part of the width of the test piece is gripped in the jaws

**4 Principle**

A test piece is extended at a constant rate of extension until it breaks. For method 1 (clause 7), the maximum force and the elongation at maximum force and, if required, the force at break and the elongation at break are determined. For method 2 (clause 8), the maximum force only is determined.

**5 Apparatus**

**5.1** *Constant rate of extension (CRE) tensile testing machine*, having the following general characteristics:

The machine shall be provided with means for reading and recording both the force applied to the test piece in stretching it to the breaking point and the corresponding extension of the test piece. It shall be provided with a strength indicator having several scales in order to ensure that the rupture of each test piece is obtained with a strength of 15 % to 85 % of the maximum of the scale used. Under conditions of use, the accuracy of the apparatus shall be class 1 as defined in ISO 7500-1. The error of the indicated or recorded maximum force at any point in the range in which the machine is used shall not exceed  $\pm 1$  %, and the error of the indicated or recorded jaw separation shall not exceed 1 mm.

After the first 2 s of the test, the rate of increase in the distance between the clamps shall be uniform to within 5 %.

If the force and elongation are recorded by means of data acquisition boards and software, the frequency of data collection shall be at least  $8 \text{ s}^{-1}$ .

**5.2** *Clamping device*, with the central point of the two jaws of the machine in the line of pull, the front edges at right angles to the line of pull and their clamping faces in the same plane. The jaws shall be capable of holding the test piece without allowing it to slip. They shall be designed so that they do not damage the test piece or reduce its strength. Smooth, flat or engraved corrugated jaws can be used for clamping. Using suitable packing materials in the jaws, e.g. paper, leather, plastics or rubber, avoids difficulties in clamping in many cases.

When tests are carried out and the test pieces either break at the jaws or tend to slip, the results may often be discarded. In order to obtain legitimate results by avoiding jaw breaks and the effect of slippage, the use of capstan jaws or any other self-locking device can be a suitable alternative to ordinary flat jaws. When information on strain is required, elongation measurements are made by means of an extensometer which follows the movements of two reference points on the test piece. The use of such jaws and an extensometer shall be reported in the test report (see 7.4, item k).

For the strip test method, the jaws shall be not less than the width of the test piece and should preferably have a width of at least 60 mm.

For the grab test method, the dimensions of one of the jaws of each clamp shall be  $25 \text{ mm} \pm 0,5 \text{ mm}$  by  $25 \text{ mm} \pm 0,5 \text{ mm}$ . The other jaw of each clamp shall be at least as wide as the one to which it is attached and should preferably be 50 mm wide.

**5.3** *Equipment for cutting test pieces and fraying them down to the required width.*

**5.4** *Equipment in which the test pieces can be immersed in water prior to wet testing.*

**5.5** *Distilled or deionized water*, for wetting out the test pieces.

**5.6** *Wetting agent or surfactant.*

**6 Atmosphere for conditioning and testing**

The atmosphere used for conditioning and testing shall be one of those specified in ISO 2231. The sample shall be conditioned for not less than 24 h.

**NOTE** If the test results are to be representative of the properties of the coated fabric at the time of manufacturing and distribution, the tests must be carried out no longer than 3 months after the date of manufacture.

**7 Method 1: strip test method****7.1 Sampling and preparation of test pieces**

From each sample, cut two sets of test pieces, one set in the longitudinal direction and the other in the transverse direction. Each set shall consist of not less than five test pieces. If, by agreement between the interested parties, a higher degree of precision is required, test more test pieces.

Select the test pieces from the full usable width and length of the sample in accordance with ISO 2286-2. An example of how test pieces may be cut out is given in Figure 4.

Each test piece shall be  $50 \text{ mm} \pm 0,5 \text{ mm}$  wide and of sufficient length to allow a distance of  $200 \text{ mm} \pm 1 \text{ mm}$  between the jaws of the test machine. If the elongation exceeds 75 %, reduce the length to  $100 \text{ mm} \pm 1 \text{ mm}$ .

If there is a woven support, take a wider strip and reduce the width to  $50 \text{ mm} \pm 0,5 \text{ mm}$  by fraying if possible. Should fraying not be possible, cut the test pieces in the direction of testing as exactly as possible along a thread.

If it is not possible to cut exactly along a thread because of distortion of the threads or the presence of an invisible support, use another test method, for example method 2.

If there is a knitted support, cut the test pieces to their final dimensions by following a wale or course. If it is not possible to cut a suitable test piece because of distortion of the threads or the presence of an invisible support, use another test method, for example method 2.

If there is a nonwoven support such as felt, cut rectangular test pieces in the longitudinal and transverse directions with tidy edges.

If tests are to be made on wet test pieces, completely immerse these for 1 h, or longer if specified, at room temperature in an aqueous solution of a wetting agent of concentration not more than 0,1 % (V/V). Rinse thoroughly in water and test within 1 min of removal from the water.

## 7.2 Procedure

### 7.2.1 Mounting the test piece in place

#### 7.2.1.1 General

Set the jaws of the test machine  $200 \text{ mm} \pm 1 \text{ mm}$  apart, or  $100 \text{ mm} \pm 1 \text{ mm}$  apart if more appropriate. Clamp a test piece in the stationary jaws so that its longitudinal axis passes through the centre of the front edge of each jaw.

Test pieces can be mounted under pre-tension or in the slack condition. When test pieces are mounted under pre-tension, check that the pre-tension does not produce an elongation greater than 5 %. If these conditions cannot be met, mount the test piece in the slack condition.

#### 7.2.1.2 Pre-tension setting

Apply the appropriate pre-tension from the following:

- a) 2 N for coated fabrics up to and including  $200 \text{ g/m}^2$ ;
- b) 5 N for coated fabrics over  $200 \text{ g/m}^2$  and up to and including  $500 \text{ g/m}^2$ ;
- c) 10 N for coated fabrics over  $500 \text{ g/m}^2$ .

#### 7.2.1.3 Slack mounting

When test pieces are mounted in the slack condition, the starting point of the curve corresponds to a 0,5 N pre-tension force. Add the corresponding elongation to the initial gauge length.

### 7.2.2 Operation

Engage any device for reading the breaking strength and elongation. Set the moving clamp in motion, at a constant rate of  $100 \text{ mm/min} \pm 10 \text{ mm/min}$  unless otherwise agreed between the interested parties, and extend the test piece to the breaking point. Repeat the procedure for each test piece.

### 7.2.3 Slippage

Disregard any test results where the test piece slips asymmetrically or slips by more than 2 mm.

When results are discarded, repeat the test on a replacement test piece taken, if practicable, from the same part of the sample as the discarded test piece.

### 7.2.4 Jaw breaks

Disregard any test results where the test piece breaks within 5 mm of the face of a jaw.

When results are discarded, repeat the test on a replacement test piece taken, if practicable, from the same part of the sample as the discarded test piece.

If, in spite of taking care, all breaks are within 5 mm of the face of a jaw, use method 2.

### 7.2.5 Tests on wet test pieces

Remove the test piece from the water (see 7.1, last paragraph), press it lightly between two sheets of blotting paper and immediately carry out the test as described in 7.2.1 to 7.2.4, except that, for the wet test, apply half the normal pre-tension.

## 7.3 Calculation and expression of results

Record the maximum force and the force at break (this has to be recorded to ascertain whether it differs from the maximum force or not) for each of the five test pieces in both the longitudinal and the transverse directions and calculate the mean value of the maximum force and the mean value of the force at break in each direction. Round both the mean maximum force and the mean force at break to the nearest 1 N or to 1 % of the calculated value. Calculate the coefficient of variation in each case and, if required, the confidence limits of the mean.

Record, to the nearest 1 mm, the elongation at maximum force (and, if different, the elongation at break) of each of the five test pieces in each direction. Express the elongation at maximum force and elongation at break values as a percentage of the distance between the jaws (200 mm or 100 mm) when a pre-tension has been applied, or as a percentage of the gauge length, correcting the gauge length for test pieces that have been slack-mounted by taking the pre-tension value from the point on the stress-strain curve corresponding to the transition from “slack” to “extension”.

Calculate the mean values of the elongation at maximum force and elongation at break. Round these mean values to the nearest 0,2 % when the mean elongation does not exceed 8 %, to the nearest 0,5 % when it is 8 % to 50 % and to the nearest 1 % when it is greater than 50 %. Calculate the coefficient of variation in each case and, if required, the confidence limits of the mean.

#### 7.4 Test report

The test report shall include the following particulars:

- a) a reference to this International Standard;
- b) the method used (method 1: strip test method);
- c) the sampling scheme used;
- d) the number of test pieces tested from each sample;
- e) the conditioning and test atmosphere used;
- f) the gauge length and the way in which the test pieces were mounted (pre-tension or slack);
- g) the state of the test pieces (conditioned or wet) and the time of conditioning or immersion;
- h) the type of tensile testing machine used and its load capacity;
- i) the values of the maximum force and, if different, the force at break, for each test piece and the mean maximum force and force at break, in newtons, for each sample, for the longitudinal and transverse directions separately, as well as the coefficient of variation for each force and each direction and, if required, the confidence limits of the mean;
- j) the values of the elongation at maximum force and, if different, the elongation at break of each test piece and the mean elongation at maximum force and elongation at break, in millimetres, for each sample, for the longitudinal and transverse directions separately, as well as the coefficient of variation and, if required, the confidence limits of the mean;
- k) details of any deviation from the specified procedure;

- l) the date of the test.

## 8 Method 2: grab test method

### 8.1 Sampling and preparation of test pieces

From each sample, cut two sets of test pieces, one set in the longitudinal direction and the other in the transverse direction. Each set shall consist of not less than five test pieces. If, by agreement between the interested parties, a higher degree of precision is required, test more test pieces.

Select the test pieces from the full usable width of the sample.

The width of each test piece shall be  $100 \text{ mm} \pm 2 \text{ mm}$  and its length shall not be less than 150 mm.

On each test piece, draw a line 37 mm from one of the long edges, parallel to the edge, along the full length of the test piece (see Figure 5).

If tests are to be made on wet test pieces, completely immerse these for a minimum of 1 h at room temperature in an aqueous solution of a wetting agent of concentration not more than 0,1 % (V/V). Rinse thoroughly in water and test within 1 min of removal from the water.

### 8.2 Procedure

#### 8.2.1 Mounting the test piece in place

Set the jaws of the test machine either  $100 \text{ mm} \pm 1 \text{ mm}$  or  $75 \text{ mm} \pm 1 \text{ mm}$  apart, by agreement between the interested parties. Clamp a test piece in the stationary jaws (5.2) so that its longitudinal axis passes through the centre of the front edge of each jaw and is perpendicular to the edges of the jaws, and so that the line drawn on the test piece coincides with the appropriate edge of each jaw (see Figure 5).

#### 8.2.2 Operation

Engage any device for reading the maximum force. Set the moving clamp in motion at a constant rate of  $100 \text{ mm/min} \pm 10 \text{ mm/min}$  unless otherwise agreed between the interested parties, and extend the test piece to the breaking point. Repeat the procedure for each test piece.

#### 8.2.3 Slippage

Disregard any test results where the test piece slips asymmetrically or slips by more than 2 mm.

When results are discarded, repeat the test on a replacement test piece taken, if practicable, from the same part of the sample as the discarded test piece.

#### 8.2.4 Jaw breaks

Disregard any test results where the test piece breaks within 5 mm of the face of a jaw.

When results are discarded, repeat the test on a replacement test piece taken, if practicable, from the same part of the sample as the discarded test piece.

### 8.2.5 Tests on wet test pieces

Remove the test piece from the water (see 8.1, last paragraph), press it lightly between two sheets of blotting paper and immediately carry out the test as described in 8.2.1 to 8.2.4.

### 8.3 Calculation and expression of results

Record the maximum force for each of the five test pieces in both the longitudinal and the transverse directions and calculate the mean value in each direction. Round the mean maximum force to the nearest 1 N or to 1 % of the calculated value. Calculate the coefficient of variation and, if required, the confidence limits of the mean.

### 8.4 Test report

The test report shall include the following particulars:

- a) a reference to this International Standard;
- b) the method used (method 2: grab test method);
- c) the sampling scheme used;
- d) the number of test pieces tested from each sample;
- e) the conditioning and test atmosphere used;
- f) the gauge length;
- g) the state of the test pieces (conditioned or wet) and the time of conditioning or immersion;
- h) the type of tensile testing machine used and its load capacity;
- i) the values of the maximum force for each test piece and the mean maximum force, in newtons, for each sample, for the longitudinal and transverse directions separately, as well as the coefficient of variation and, if required, the confidence limits of the mean;
- j) details of any deviation from the specified procedure;
- k) the date of the test.

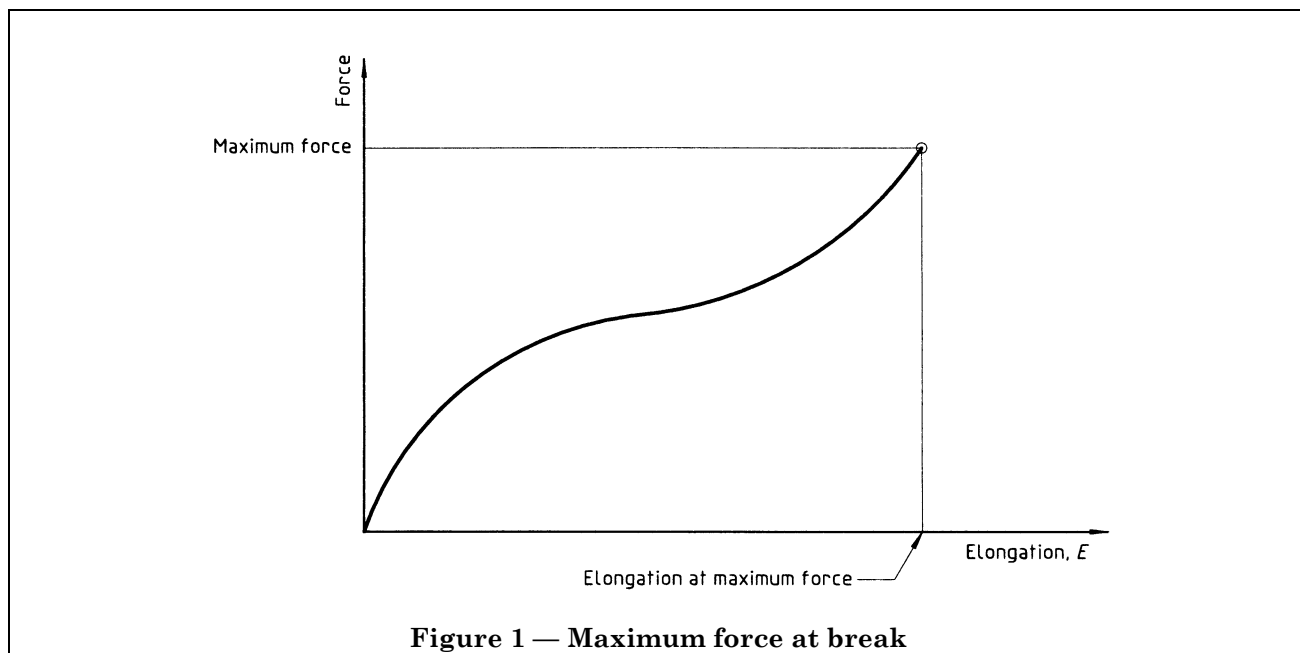


Figure 1 — Maximum force at break

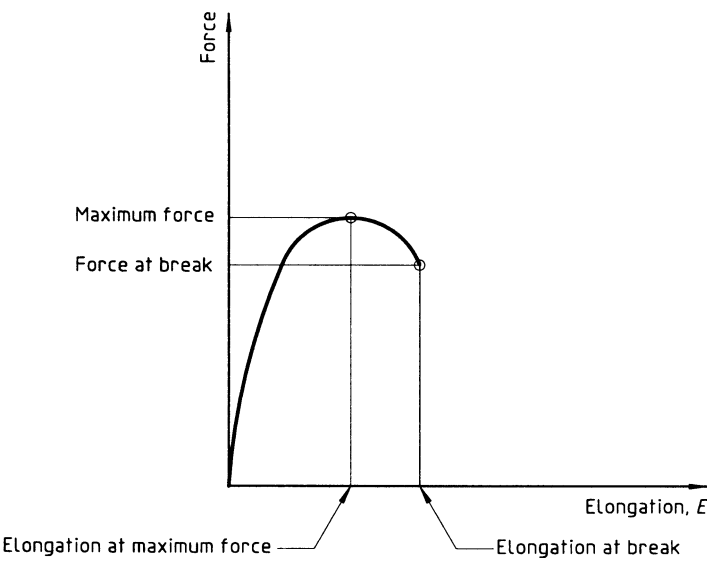


Figure 2 — Tensile force at break



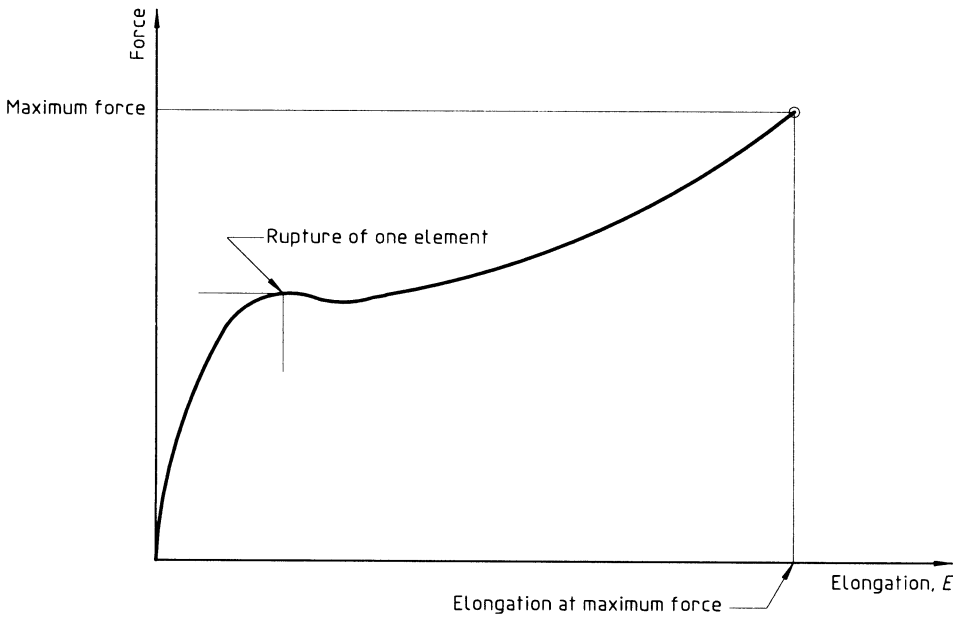


Figure 3 — Rupture of one element of a coated fabric

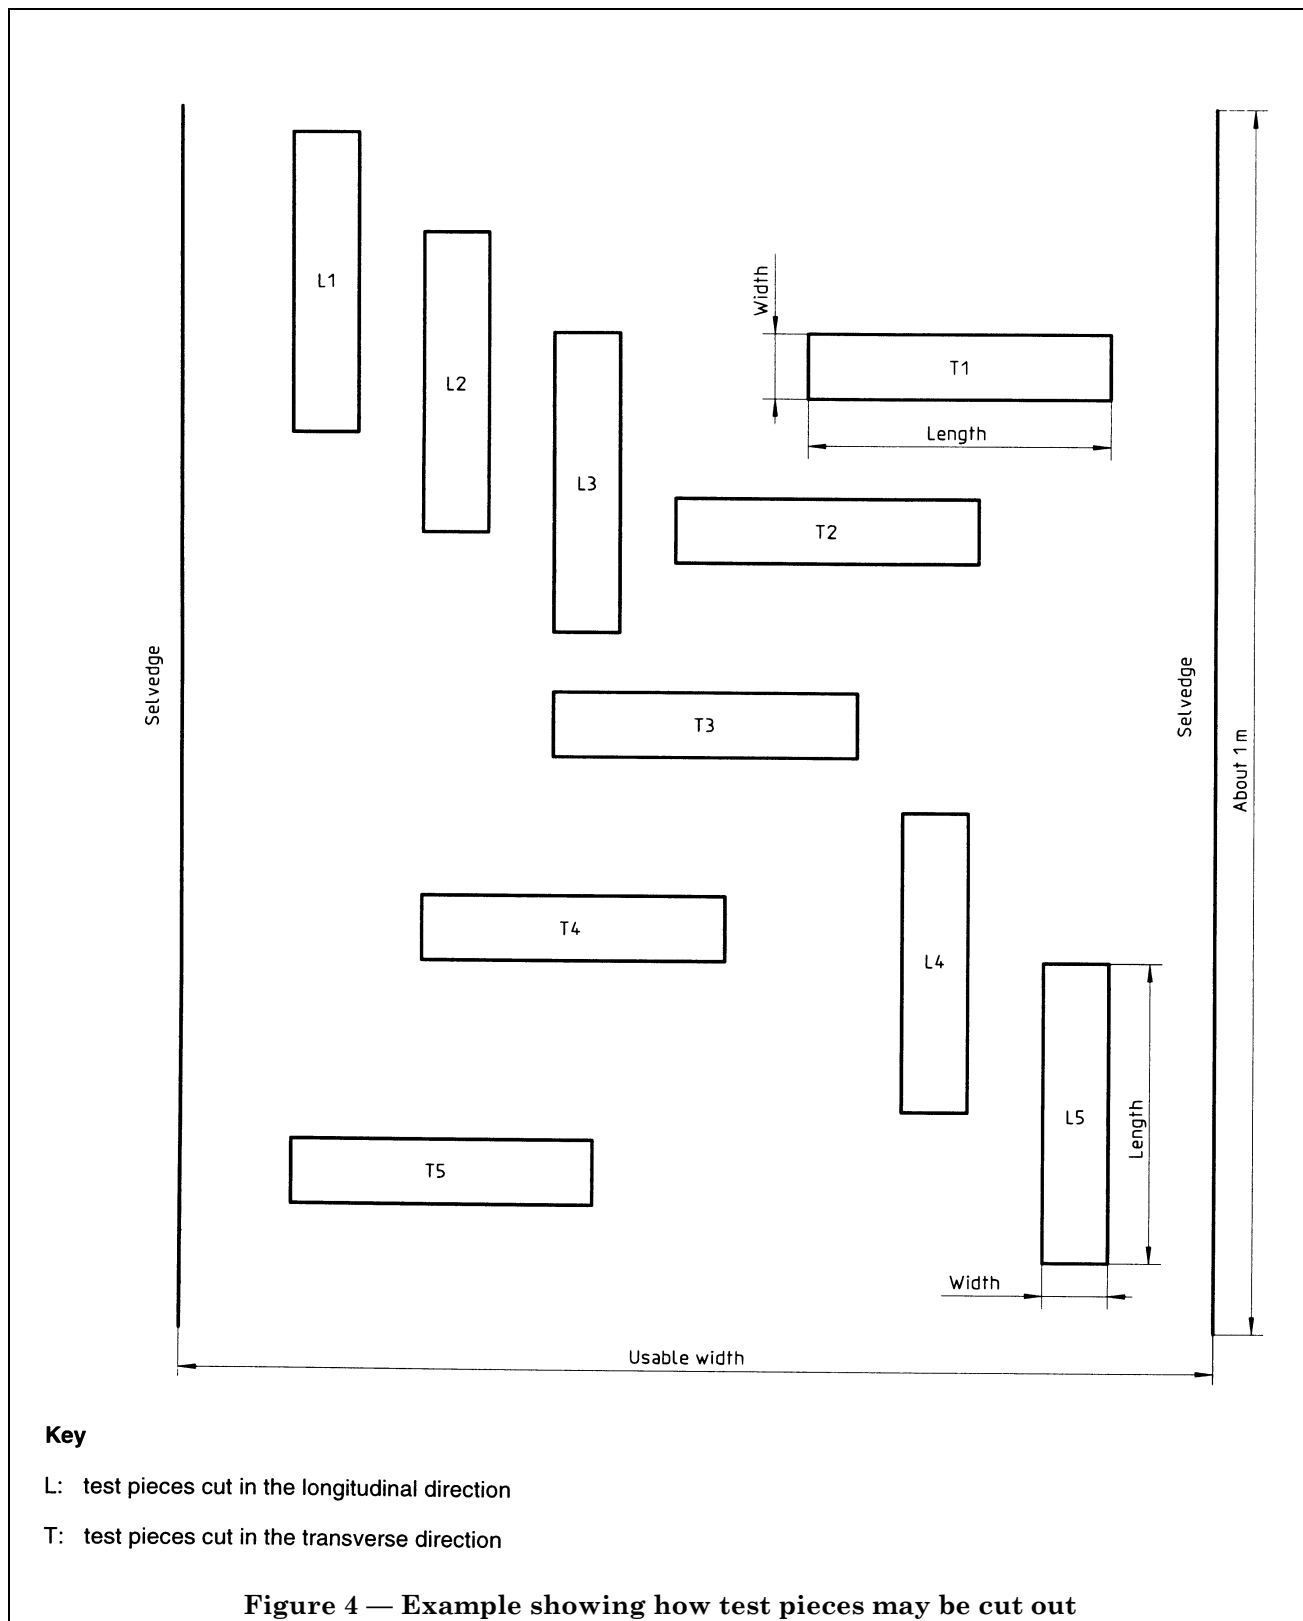

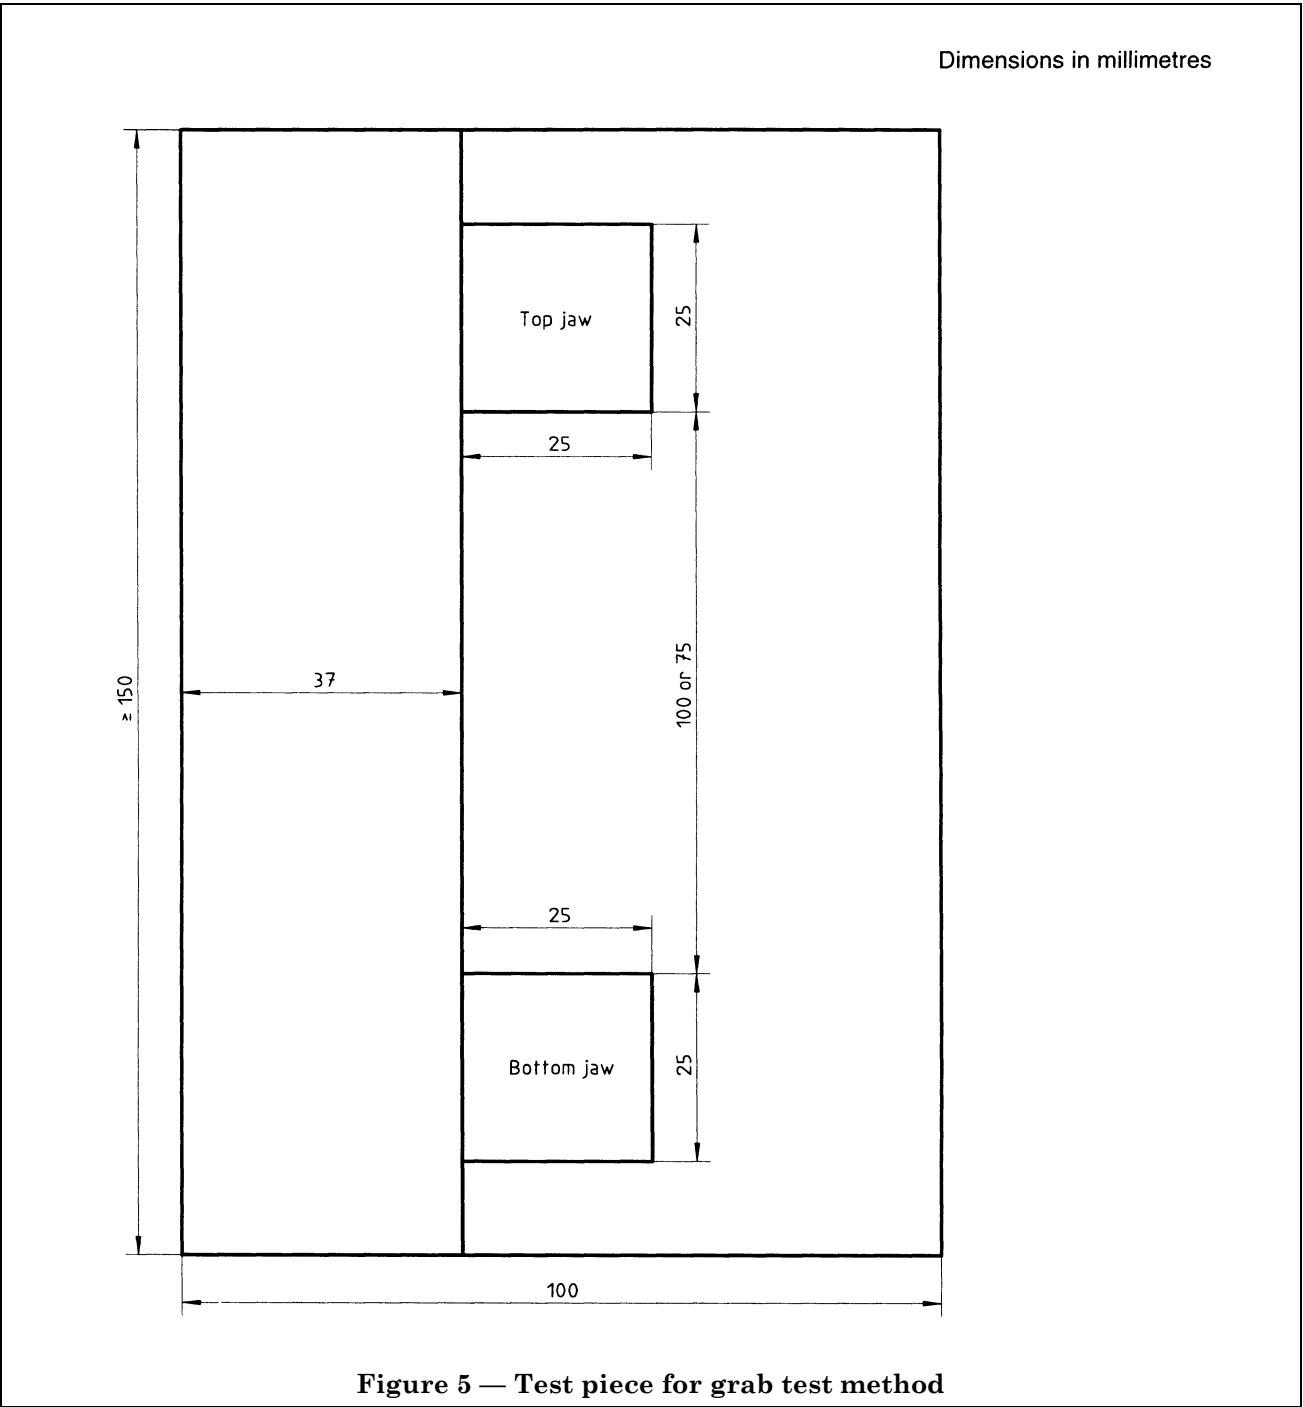

**Annex ZA (normative)****Normative references to international publications with their relevant European publications**

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

| <b>Publication</b> | <b>Year</b> | <b>Title</b>   | <b>EN</b>   | <b>Year</b> |
|--------------------|-------------|--|-------------|-------------|
| ISO 2231           | 1989        | Rubber- or plastics-coated fabrics — Standard atmospheres for conditioning and testing | EN ISO 2231 | 1995        |

---

## **BSI — British Standards Institution**

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### **Revisions**

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### **Buying standards**

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### **Information on standards**

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

### **Copyright**

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.